



# Novel poly(3-hydroxy butyrate) macro RAFT agent. Synthesis and characterization of thermoresponsive block copolymers

Baki Hazer<sup>1,2</sup> · Melike Eren<sup>2</sup> · Yetkin Senemoğlu<sup>2</sup> · Tina Modjinou<sup>3</sup> · Estelle Renard<sup>3</sup> · Valérie Langlois<sup>3</sup>

Received: 16 December 2019 / Accepted: 22 April 2020  
© The Polymer Society, Taipei 2020

## Abstract

A novel reversible addition fragmentation transfer (RAFT) agent based on the poly-3-hydroxy butyrate (PHB) with three hydroxyl groups (PHB-R2) and thermoresponsive amphiphilic block copolymers derived from N-isopropyl acryl amide (NIPAM) are described. Hydroxylated PHB is obtained by the reaction between PHB and diethanol amine (DEA) to prepare hydroxylated PHB (PHB-DEA). It is then reacted with a RAFT agent, 2-(dodecylthiocarbonothioylthio)-2-methylpropionic acid (DDMAT). Hydroxyl ends of the hydroxylated PHB are capped with carboxylic acid end of the trithiocarbonate. The block copolymers obtained by the polymerization of NIPAM initiated by PHB-R2 were characterized by <sup>1</sup>H NMR and physicochemical techniques. PHB content in the obtained block copolymers is varying between 14 and 45 wt%. The thermo-responsive PHB-PNIPAM block copolymers show the lower critical solution temperature (LCST) 28 and 30 °C while LCST of the pure PNIPAM is 32 °C.

**Keywords** Poly (3-hydroxy butyrate) · RAFT polymerization · Polymerization kinetics · Thermoresponsive polymer · PNIPAM

## Introduction

Some microorganisms accumulate poly(3-hydroxy alkanic acid) (PHA) into their cell as energy reserve material from carbon sources [1]. Regarding pendant groups, PHA can be classified in three types: short chain length (scl) PHA, medium chain length (mcl) PHA and long chain length (lcl) PHA [2–8]. However, they need modification reactions because of their limited properties for industrial and medical applications [9–16].

PHAs are biodegradable, biocompatible hydrophobic semi crystalline polyesters. Mcl-PHAs are soft elastomeric polyesters and show low thermal resistant (ca.  $T_m$  50 °C) while scl-

PHAs are brittle solid materials and show higher thermal resistance (ca.  $T_m$  170 °C). There are fine modification reactions to enhance hydrophilicity of the mcl-, and scl-PHAs. Among them, thiol-ene reactions [17, 18], esterification with PEG [19, 20], water soluble PHA-sulfonate [21, 22], and aminolysis reactions [23] were successfully used in order to obtain mcl-PHA with enhanced hydrophilicity.

There are some modification reactions of mcl-PHAs. In a combined reaction of thiol terminated poly (N-isopropyl acryl amide) (PNIPAM) with thiol-ene reaction of unsaturated mcl-PHA results in a thermoresponsive copolymer of PHA. In this manner, chain transfer agent terminated poly (N-isopropyl acryl amide) (PNIPAM) converted to PNIPAM with thiol end is used in the thiol-ene click reaction with a random copolymer of 3-hydroxydodecanoate (3HDD) and 3-hydroxy-10-undecylenate [24]. In a recent work, a novel elastomer, polystyrene copolymer of a mcl-PHA, have been described [25]. There are also some reports on PHB modification reactions. Chlorination reactions of PHB result in chloride derivative of PHB for further modification reactions [26, 27]. A recent published article reports optical properties of blend of the chlorinated PHB and PMMA [28]. PEG is a hydrophilic and biocompatible polymer. It is widely used in preparation of amphiphilic PHB derivatives [29]. Atom transfer radical polymerization of NIPAM and dimethyl amino ethyl

✉ Baki Hazer  
bhazer2@yahoo.com; bkhazer@beun.edu.tr

✉ Valérie Langlois  
langlois@icmpe.cnrs.fr

<sup>1</sup> Department of Aircraft Airframe Engine Maintenance, Kapadokya University, 50420 Ürgüp, Nevşehir, Turkey

<sup>2</sup> Department of Chemistry, Department of Nano Technology Engineering, Bülent Ecevit University, 67100 Zonguldak, Turkey

<sup>3</sup> CNRS, Inst Chim & Mat Paris Est, UMR 7182, 2-8 Rue Henri Dunant, University of Paris Est, F-94320 Thiais, France

methacrylate initiated by brominated PHB-macroinitiator rendered the related responsive block copolymers which could be used for the encapsulation and release of therapeutic drugs in the biological systems [30, 31]. Dihydroxylated PHB (PHB-diol) prepolymer is prepared by transesterification from the natural PHB with 1,10-decane diol [32] and diethylene glycol [33]. Multiblock-elastomeric PHB-PEG-PHO copolymers can be obtained by the amination reaction of PHB with the amine terminated PEG [34]. Recently, hydroxylated PHB (PHB-DEA) was derived from the PHB and diethanol amine. Then, a radiopaque biodegradable polymer was obtained by the capping reaction of hydroxyl ends of PHB-DEA with iodo benzoyl chloride [35]. In this work, hydroxyl ends of the PHB-DEA were capped with the carboxylic acid end of the tri thio carbonate, 2-(dodecyl thio carbonothioylthio)-2-methylpropionic acid. RAFT polymerization of NIPAM initiated by PHB-macro RAFT agent, resulted in PHB-PNIPAM thermoresponsive amphiphilic graft copolymers. Physicochemical characterization of series of the PHB-PNIPAM thermoresponsive block copolymers were characterized by  $^1\text{H}$  NMR and physicochemical methods.

## Experimental

### Materials

Poly (3 - hydroxy butyrate) (PHB), microbial polyester ( $M_n$  187,000 g/mol,  $M_w/M_n$  2.5, Biomer Inc.) was supplied from BIOMER (Germany) [36]. 2-(Dodecylthiocarbonothioylthio)-2-methylpropionic acid (DDMAT) was synthesized according to the procedure in cited reference [37]. Dimethyl formamide (DMF),  $N,N'$ -dicyclohexylcarbodiimid (DCC), dimethyl amino pyridine (DMAP), stannous 2-ethyl hexanoate (Sn-oct), diethanol amine (DEA),  $N$ -isopropyl acryl amide (NIPAM),  $\text{NaBH}_4$  and the other chemicals were purchased from Sigma-Aldrich. NIPAM was crystallized from boiling n-hexane before use.

### Synthesis of PHB-DEA

Hydroxylated PHB was obtained by the reaction of PHB with DEA according to the procedure reported in the cited reference [35]. Briefly: A mixture of 60.3 g of vacuum dried PHB, 102 g of DEA and 2.1 g of Sn-oct in 250 mL of  $\text{CHCl}_3$  was stirred at room temperature for 24 h. Then, it was refluxed for 3 h. The solvent was distilled under atmospheric condition (not in the rotary evaporator). Then the crude product was cured in 125 °C for 30 min. The product was leached with excess methanol and filtered. The crude product was dried under vacuum at 40 °C. For further purification, the obtained polymer was dissolved in 600 mL of  $\text{CHCl}_3$  and filtered. The solvent was evaporated in a rotary evaporator. The obtained

polymer was leached excess methanol again. Methanol was removed via filtration. The pure PHB-DEA was dried under vacuum at 40 °C for 24 h. Yield was 36 g. This was coded as PHB-DEA-13. Characteristic FTIR signals: 1567  $\text{cm}^{-1}$  amide carbonyl; 3301  $\text{cm}^{-1}$  primary hydroxyl groups of DEA; 1721  $\text{cm}^{-1}$  belongs to ester carbonyl of PHB. The characteristic chemical shifts of the PHB-DEA sample in  $^1\text{H}$  NMR spectrum were observed at 1.3 ppm for  $-\text{CH}_3$ , 2.4–2.6 ppm for  $-\text{CH}_2-\text{COO}-$ , 3.0 ppm for  $-\text{N}-\text{CH}_2-$ , 3.5–3.8 ppm for  $-\text{CH}_2-\text{OH}$ , 4.1 ppm for  $-\text{CH}-\text{OH}$  and 5.1–5.3 ppm for  $-\text{CH}-\text{O}-$ .

### Synthesis of PHB macro-raft agent (PHB-mR)

The PHB-macro-RAFT agent (PHB-R2–131) was obtained by the reaction between PHB-DEA-22 and 2-(Dodecylthiocarbonothioylthio)-2-methylpropionic acid (DDMAT), using the procedure reported by Steglich esterification method [38]. Briefly, PHB-DEA-22 (9.8 g) was dissolved in a mixture of  $\text{CH}_2\text{Cl}_2$  (100 mL) and DMF (5 mL). To this solution were added continuously stirring DDMAT (6.3 g, 0.017 mol), DCC (9.2 g, 0.045 mol) and DMAP (0.81 g, 0.0066 mol) under Argon. After stirred at room temperature for 24 h, the precipitated side product, dihexyl urea, was filtered. The solvent of the filtered solution was evaporated, the crude product was leached with excess methanol, and the PHB-R2 was purified via filtration. The white solid product was dried under vacuum at 40 °C for 24 h. The GPC result (in DMF) was  $M_n$  3800 Da,  $M_w$  4700 Da, PDI 1.225.

### RAFT polymerization of NIPAM initiated by PHB-R2

RAFT polymerization of NIPAM was carried out at 80 °C in DMF. For example, the mixture of 0.507 g of PHB-R2, 19 mg of AIBN and 1.22 g of NIPAM was dissolved in 5 mL of DMF in a glass bottle. Argon was introduced through a needle into the tube for about 1 min to expel the air. The tightly capped bottle was then put into a water bath at 80 °C for 220 min. Then, the crude polymer solution diluted with 5 mL of  $\text{CHCl}_3$  was precipitated in 200 mL of methanol. The graft copolymer samples were dried overnight under vacuum at 40 °C for 24 h. The dried copolymer (1.0 g) was stirred in THF (20 mL) for 2 h. The mixture was filtered from the insoluble copolymer residue. PHB-PNIPAM copolymer was isolated by evaporating the solvent. The THF soluble polymer was dried under vacuum at 40 °C for 24 h.

### Characterization

**$^1\text{H}$  NMR and FT-IR**  $^1\text{H}$  NMR spectra of the obtained products were taken at 25 °C with an Agilent NMR 600 MHz NMR (Agilent, Santa Clara, CA, USA) spectrometer equipped with a 3 mm broadband probe. Acquisition parameters included a

45° hard pulse angle, a sweep width of 14 ppm, 1.7 s acquisition time, 0.1 s pulse delay and continuous WALTZ - 16 broadband 1H decoupling. Up to 2000 scans were collected per sample, corresponding to ~1 h of collection time. FT- IR spectra of the polymer samples were recorded using Perkin-Elmer FT - IR Spectrometer 100.

**Size exclusion chromatography (SEC) analysis** Two different SEC instruments were used in this work; eluents were THF and DMF, separately. For THF eluent, molecular weights were determined by size exclusion chromatography instrument, Viscotek GPCmax Auto sampler system, consisting of a pump, three ViscoGEL GPC columns (G2000H HR, G3000H HR and G4000H HR), and a Viscotek differential refractive index (RI) detector with a THF flow rate of 1.0 mL/min at 30 °C. A calibration curve was generated with four polystyrene (PS) green standards: 8450, 2960, 50,400, 200,000 and 696,500 Da, of low polydispersity. The polymer sample solution containing 0.05 g in 10 mL of THF was filtered and injected automatically into the instrument. Data was analyzed using Viscotek Omni SEC Omni 01 software.

Another Size Exclusion Chromatography using DMF as eluent with Flow rate 0.5 mL/min was also used. It was TOSOH EcoSEC – WYATT HELEOS-II – WYATT DynaPro Nanostar GPC System using. Column: Tosoh HHR5000-HHR3000-HHR Guard Column Set. Low polydispersity index polystyrene standards purchased from Polysciences were used to calibrate the system (483,000; 184,900; 60,450; 19,720; 8450; 3370, 580 g.mol<sup>-1</sup>). The

samples were dissolved at a concentration of 10 mg.mL<sup>-1</sup> and filtered on a PTFE filter of 0.5 µm prior analysis.

**Thermal analysis** Thermal analysis of the obtained polymers was carried out under nitrogen using a TA Q2000 DSC and Q600 Simultaneous DSC - TGA (SDT) series thermal analysis systems. Differential Scanning Calorimeters (DSC) measures temperatures and heat flows associated with thermal transitions in the polymer samples obtained. The dried sample was heated from - 60 to 120 °C under nitrogen atmosphere heating from 20 to 600 °C at a rate of 10 °C/min.

The mass loss of the samples was determined by TGA under nitrogen atmosphere using a Setaram Labsys Evo 1150 apparatus by heating from 30 °C to 550 °C at 10 °C.min<sup>-1</sup>.

Proton NMR spectra in CDCl<sub>3</sub> solutions of the samples were taken at a temperature of 25 °C with an Agilent NMR 600 MHz NMR (Agilent, Santa Clara, CA, USA) spectrometer equipped with a 3 mm broadband probe.

**LCST determination** At fixed temperature, vacuum dried copolymer film (200 mg) was soaked into water. After 3 h, the swollen polymer film gently wiped with a paper tissue and weighed. The water uptake of the film was calculated using the following equation:

$$\text{Water uptake (WT\%)} = \frac{(m_s - m_d)}{m_d} \times 100 \quad (1)$$

Where,  $m_s$  is weight of swollen polymer film and  $m_d$  is weight of dried polymer film.


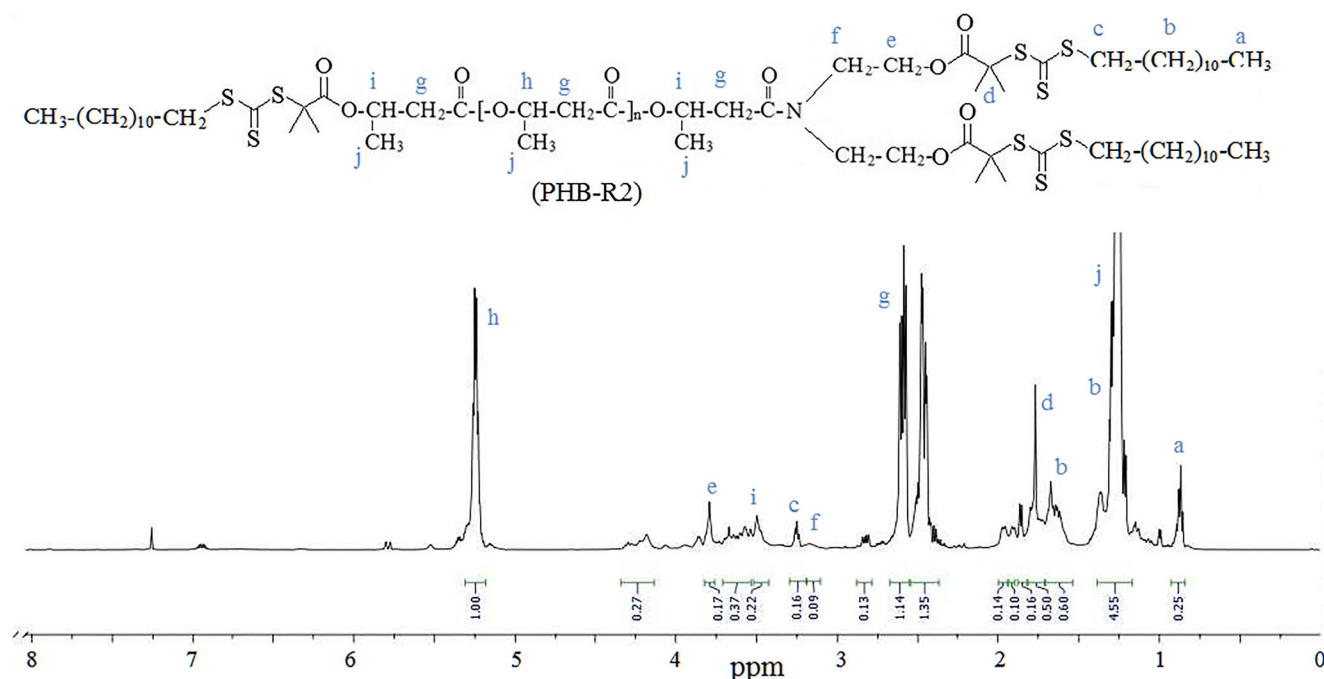


Fig. 1 <sup>1</sup>H NMR spectrum of the PHB-macro raft agent, PHB-R2

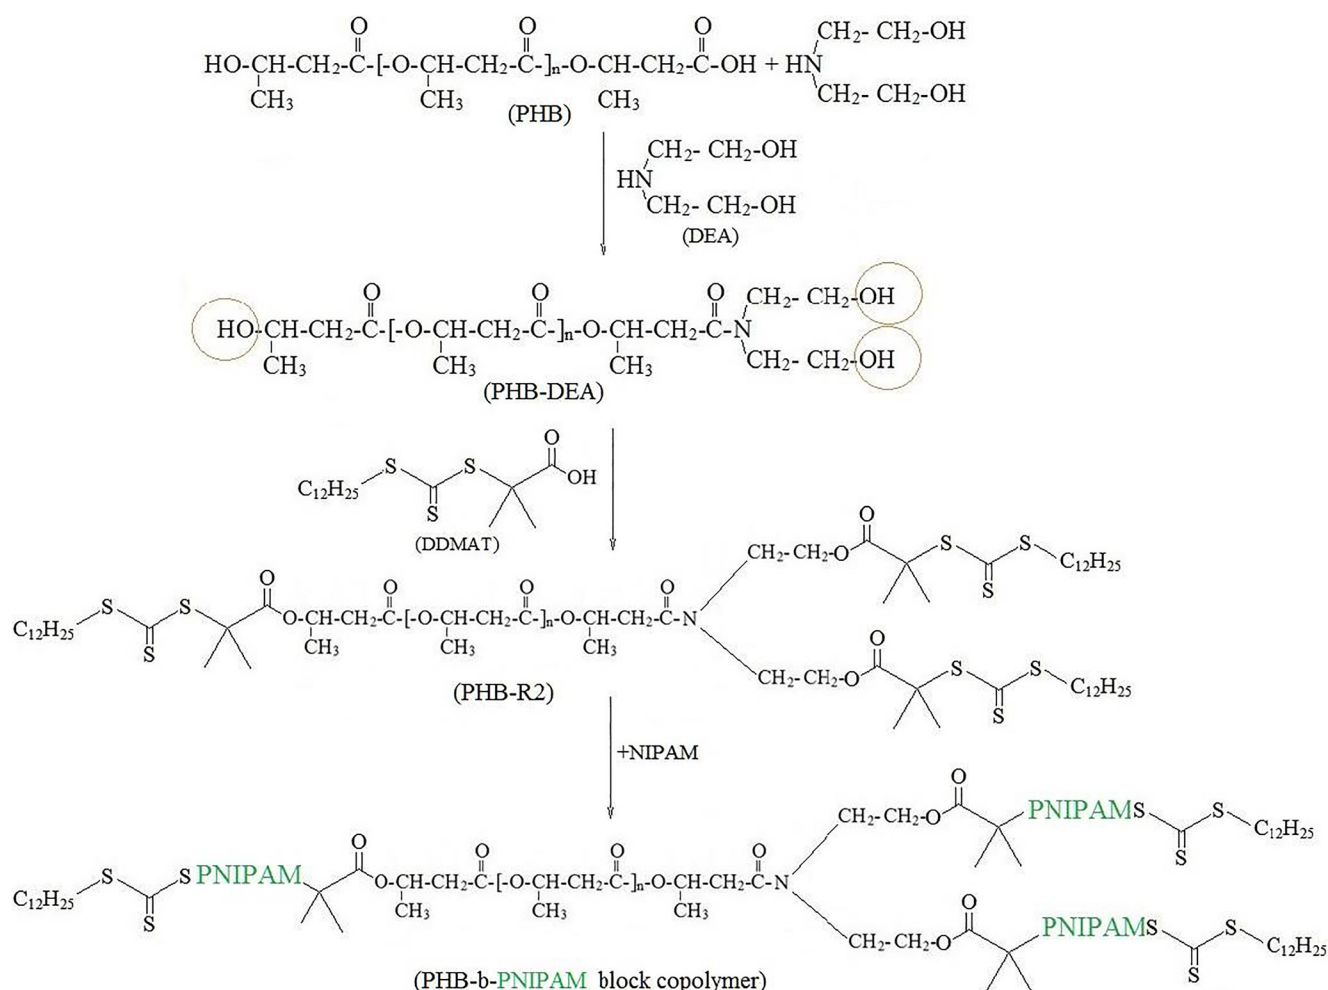

**Scheme 1** Reaction steps for the synthesis of the PHB-R2 macro raft agent

The same swelling procedure was repeated at 4, 22, 27, 29, 32, and 34 °C. Water uptake against temperature was plotted. The strong drop in sigmoidal curve offers us LCST for this thermoresponsive copolymer.

**Micelle formation and dynamic light scattering analysis**  
Micelles were prepared according to the Cheng [39] method.


10 mg of the PHB-PNIPAM-6 were dissolved in 1 mL of DMF under stirring during 2 h. Then, 10 mL of Milli-Q ultra purified water were added dropwise to the solution under stirring. After 3 h of stirring at room temperature, the DMF was removed by dialysis against water for 3 days.

DLS measurements were performed at 633 nm on a Malvern Instrument Zetasizer Nano ZS provided with a He-

**Table 1** RAFT polymerization of NIPAM using PHB-R2 macro raft agent (0.50 g) and AIBN (20 mg) in 5 mL of DMF at 80 °C for 205 min. (\*calculated from their NMR spectra)

| Code         | PHB-R2<br>(wt%) | NIPAM |     | Copolymer Yield<br>(g) | Mn<br>(D) | Mw<br>(D) | Copolymer Yield<br>PDI | PHB content* in cop.(%) |
|--------------|-----------------|-------|-----|------------------------|-----------|-----------|------------------------|-------------------------|
|              |                 | (g)   | wt% |                        |           |           |                        |                         |
| PHB-PNIPAM-0 | 50              | 0.51  | 50  | 0.84                   | 5400      | 6600      | 1.2                    | 45                      |
| PHB-PNIPAM-1 | 29              | 1.22  | 71  | 1.67                   | 9900      | 11,200    | 1.1                    | 33                      |
| PHB-PNIPAM-2 | 18              | 2.25  | 82  | 2.61                   | 14,700    | 16,800    | 1.1                    | 24                      |
| PHB-PNIPAM-3 | 12              | 3.84  | 88  | 3.69                   | 15,600    | 19,300    | 1.2                    | 18                      |
| PHB-PNIPAM-4 | 9               | 5.20  | 91  | 4.77                   | 16,600    | 20,600    | 1.2                    | 14                      |
| PHB-R2       |                 |       |     |                        | 3800      | 4700      | 1.2                    | (in DMF)                |

**Fig. 2**  $^1\text{H}$  NMR spectra of the obtained PHB-PNIPAM block copolymers

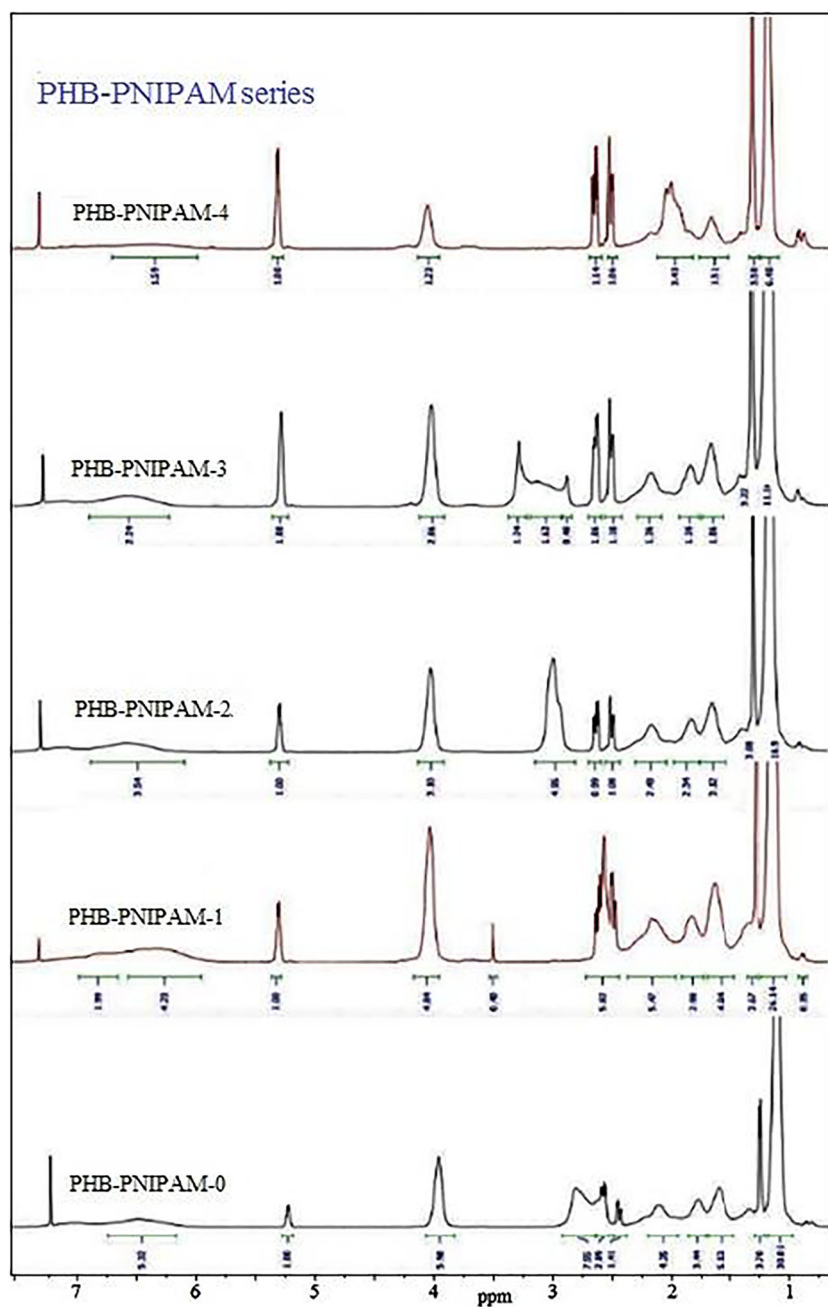


Ne laser source. Measurements were conducted at an angle of  $173^\circ$  at  $25^\circ\text{C}$ . The cumulant method was used to analyze the autocorrelation functions to determine dimeters and distributions.

## Results and discussion

The main objective of this work is to prepare a new PHB-macro RAFT agent and to study the polymerization of NIPAM. For this purpose, we started with the synthesis of


hydroxylated PHB using DEA to prepare the novel macro RAFT agent. PHB was refluxed with DEA and stannous octoate as catalyst in chloroform in an oil bath at  $80^\circ\text{C}$ , after solvent was distilled; PHB-DEA crude product was cured at  $125^\circ\text{C}$  for 30 min. During the hydroxylation process at least 20% of the starting material remains undissolved in chloroform. The unreacted starting material was removed from the chloroform solution via filtration [32]. Then, the hydroxyl ends of the pure PHB-DEA were capped with DDMAT using Steglich reaction process. Because, trithiocarbonate (DDMAT) have been previously shown to be effective for

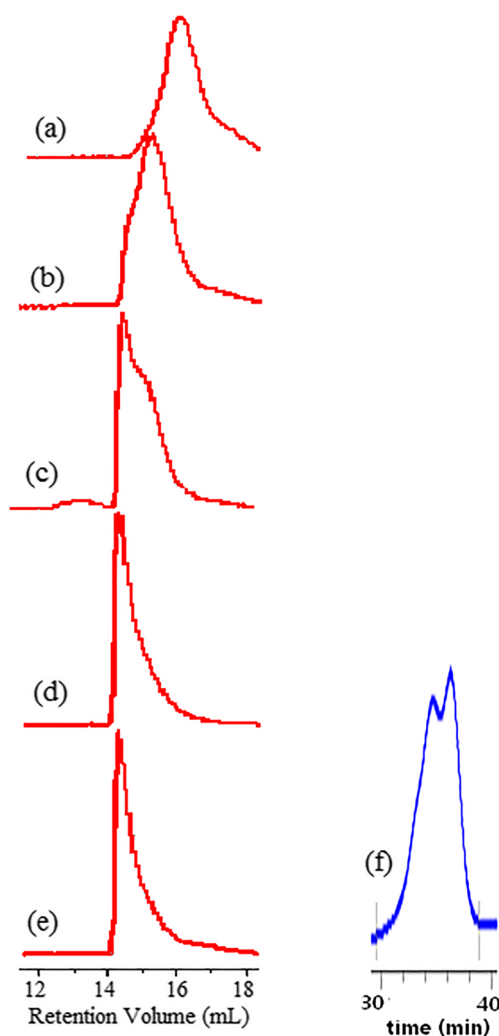

**Fig. 3** SEC measurements of the PHB-PNIPAM block copolymers: **a** PHB-PNIPAM-0, **b** PHB-PNIPAM-1, **c** PHB-PNIPAM-2, **d** PHB-PNIPAM-3, **e** PHB-PNIPAM-4, **(f)** PHB-R2

the controlled polymerization of a variety of monomers [40]. The characteristic signals of PHB-macro RAFT agents (PHB-R2) were observed in its  $^1\text{H}$  NMR spectrum. Figure 1 shows the all labeled signals of the macro RAFT agent. The characteristic signals of the PHB-RAFT agent in the  $^1\text{H}$  NMR spectra were observed:  $\delta$  ppm: for PHB blocks: 1.25 ( $-\text{CH}_3$ , j), 2.5 [ $-\text{CH}_2-\text{C}(\text{O})-$ , g], 5.25 ( $-\text{CH}-\text{O}-$ , h); for DEA units: 3.1 ( $-\text{N}-\text{CH}_2-$ , f), 3.8 ( $-\text{CH}_2-\text{O}-$ , e); for the trithiocarbonate units 0.85 ppm ( $\text{CH}_3$ , a), 1.65 ppm [ $-(\text{CH}_2)_{10}-$ , b], 1.75 ppm [ $-\text{C}(\text{CH}_3)_2$ , d], 3.25 ppm ( $-\text{S}-\text{CH}_2-$ , c).

**Synthesis of PHB-NIPAM thermoresponsive copolymers** PHB macro RAFT agent was used in RAFT polymerization of NIPAM as chain transfer agent at  $80^\circ\text{C}$ . Scheme 1 shows the reaction steps of the RAFT polymerization of NIPAM by PHB-R2 and AIBN at  $80^\circ\text{C}$ . A series of the block copolymers were obtained by the RAFT polymerization of NIPAM using different amount of PHB-R2 at  $80^\circ\text{C}$ . The ratio of the RAFT

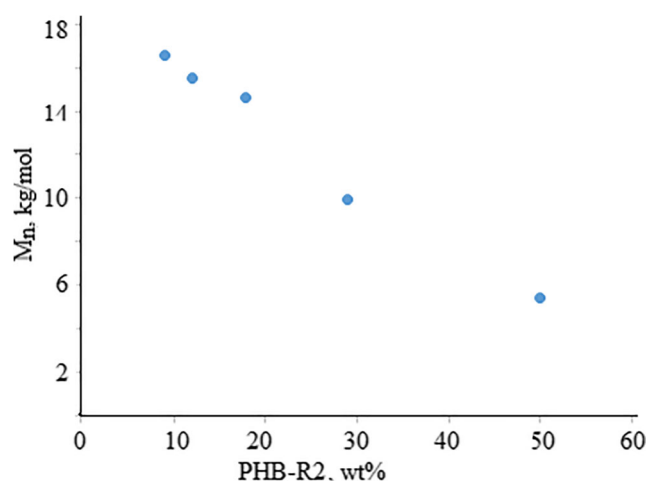


**Fig. 4** RAFT polymerization of NIPAM. Variation of PHB-R2 concentration (wt%) in feeding against molar masses of the obtained copolymers

agent to AIBN was varying from 25/1 to 55/1 while polymerization time was kept at 205 min.

Polymerization conditions and results were listed in Table 1. PHB content in the beginning was proportional with the PHB content in copolymer determined from their NMR spectra. Small difference in PHB content may come from that NIPAM monomer used in the beginning does not convert to polymer completely. Then the PHB content is found to be slightly higher than the beginning one. In case of the highest concentration of PHB, the slightly less PHB content was observed. Presumably, some degraded PHB copolymer can be solubilized in non-solvent media.

$^1\text{H}$  NMR technique was used for the structural analysis of the obtained PHB-PNIPAM block copolymers. As expected, PHB inclusion of the obtained copolymer was proportional with the PHB-R2 used in feeding. Figure 2 shows the comparative  $^1\text{H}$  NMR spectra of the copolymer series. As macro RAFT agent, PHB-R2, decreases in feeding, much PNIPAM but low PHB introduces into the obtained copolymer. PHB contents in the obtained copolymers were calculated by comparing chemical shifts at 5.2 ppm ( $-\text{CH}-\text{O}-$ , PHB) with 4.0 ppm ( $>\text{CH}-\text{NH}-$ , PNIPAM) in their  $^1\text{H}$  NMR spectra. The calculated PHB contents in the obtained copolymers were listed in Table 1 as well.

We used SEC instrument with eluent THF for the THF soluble PHB-PNIPAM -0-5 series. PHB-R2 was soluble in DMF as eluent, and then we used another SEC instrument with eluent DMF. For the PHB-PNIPAM series, molar masses were measured in range between from 5400 to 16,600 Da while molar mass of PHB-R2 chain transfer agent 3800 Da. SEC results and the PHB contents in the copolymers were tabulated in Table 1. The GPC chromatograms of the obtained PHB-PNIPAM block copolymer -0-4 series can be seen in Fig. 3. There are smooth correlation with PHB contents in feeding composition and molar masses. Increase in NIPAM

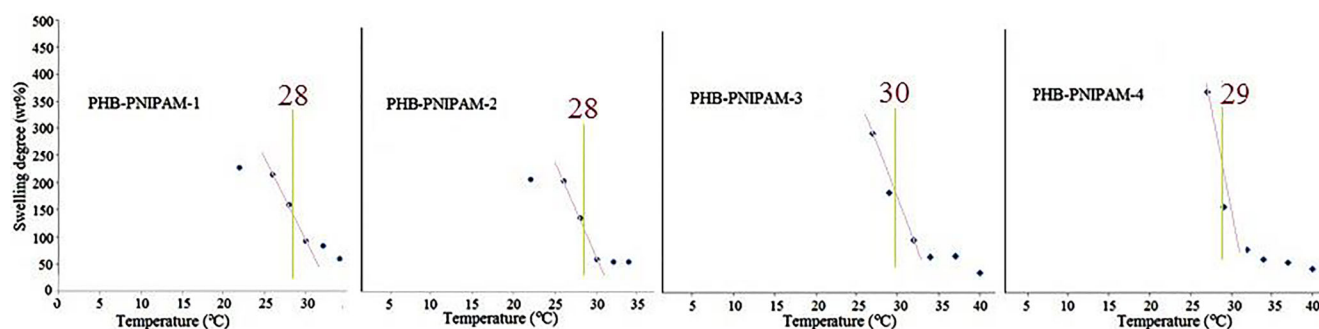


**Fig. 5** Variation of the swelling degrees in water against temperature: PHB-PNIPAM-1, -2, -3, and -4

feeding causes increase in polymer yield and increase in molar mass. The dispersity is around 1.2 for monomer conversions above 40%. Interestingly, SEC analyses revealed bimodal molar mass distributions for some samples. One could speculate that the PHB-R2 chain transfer agent can behave with varying

activity in the monomer solution, which clearly requires extensive additional studies [41].

In this manner, in the highest PHB-R2 concentration leads to copolymer with the lowest  $M_n$  (5400 g/mol) while the lowest concentration of the raft agent yields the block copolymer with

**Fig. 6** TGA analysis of the PHB-PNIPAM samples

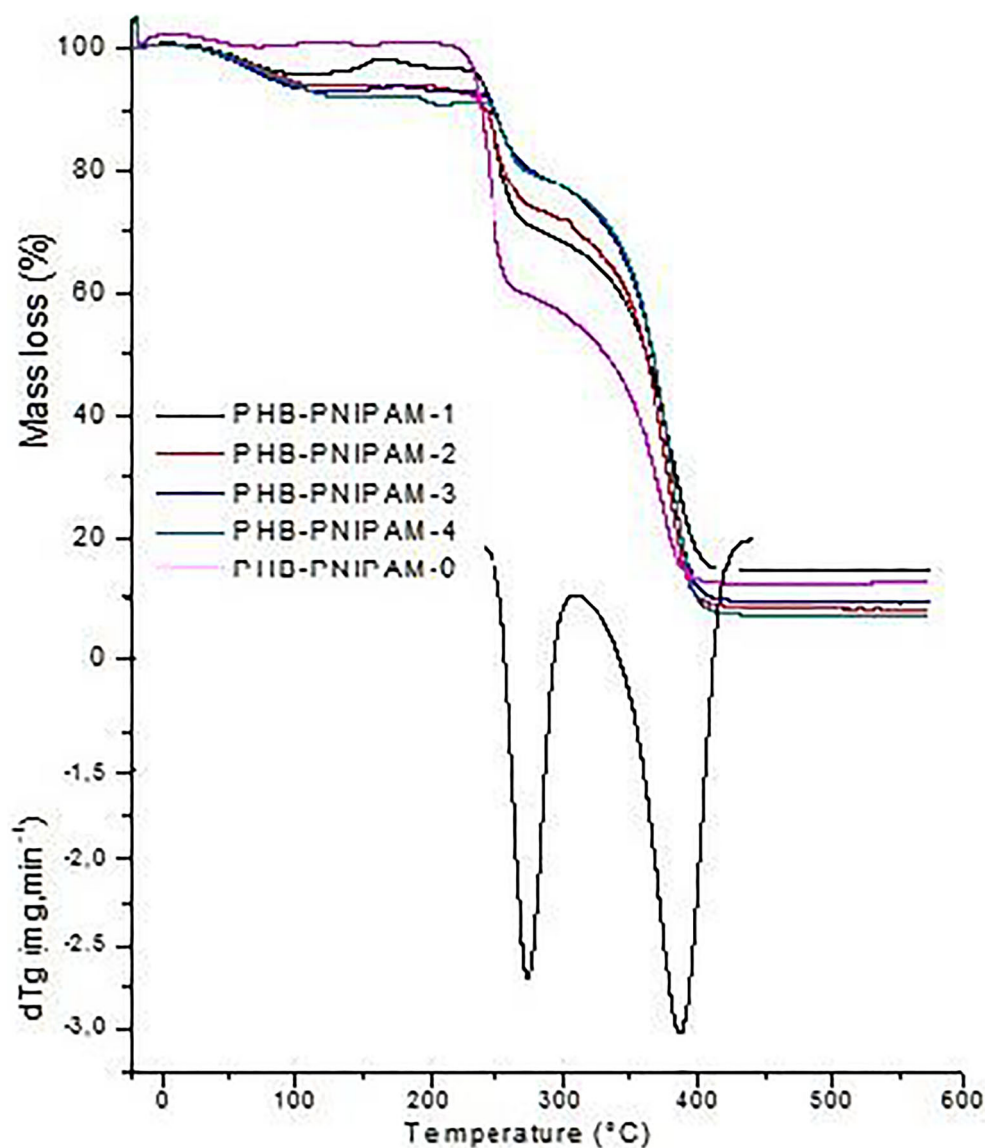

**Table 2** Results of the thermogravimetric analysis of the PHB-PNIPAM samples

| Sample       | T <sub>d1</sub> 245 °C<br>(wt loss%) | T <sub>d2</sub> 380 °C<br>(wt loss%) |
|--------------|--------------------------------------|--------------------------------------|
| PHB-PNIPAM-0 | 44                                   | 45                                   |
| PHB-PNIPAM-1 | 27                                   | 55                                   |
| PHB-PNIPAM-2 | 20                                   | 65                                   |
| PHB-PNIPAM-3 | 14                                   | 70                                   |
| PHB-PNIPAM-4 | 11                                   | 73                                   |


the highest Mn (16,600 g/mol). Figure 4 shows the variation of the macro RAFT agent concentration (PHB-R2, wt%) in feeding against the molar masses of the obtained block copolymers.

Lower critical solution temperatures of PHB-PNIPAM block copolymers were determined by the swelling measurements at the temperatures between from 40 to 22 °C. The

samples had the LCSTs between 28 to 30 °C. The enhanced hydrophobicity leads to lower LCST of NIPAM [42]. Variation of the swelling degrees in water against temperature can be seen in Fig. 5.


**Thermogravimetric analysis** The PHB-PNIPAM0–4 samples were found to be thermally stable below 200 °C, exhibiting two main weight loss steps (Fig. 6). The evaporation of the small and soluble compounds was observed at lower temperature than 240 °C. The first stage of degradation with a T<sub>max</sub> of 260 °C occurs between 245 and 300 °C can be attributed to the thermal degradation of PHB main chains. The second stage of degradation with a T<sub>max</sub> of 380 °C associated to the weight loss of PNIPAM blocks occurs between 300 and 420 °C. The TGA results can be seen in Table 2.

**Micelle formation** PHB-PNIPAM copolymers were synthesized by RAFT mechanism. The solution behaviors of some

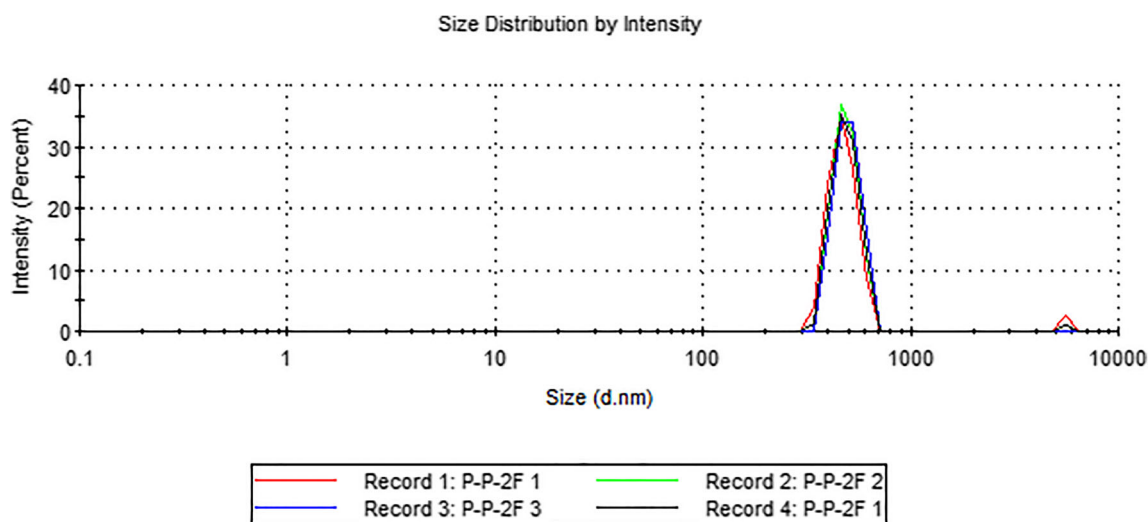**Fig. 7** Particle size distribution analyzed by dynamic light scattering (DLS) of PHB-PNIPAM-2 before filtration**Table 3** Polymerization of NIPAM (500 mg, 2.21 M) initiated by PHB-R2: 200 mg (26 mM), AIBN: 8 mg, DMF: 2.0 mL, at 70 °C)

| Code          | Time<br>(min) | Yield<br>(mg) | Conv.<br>(%) | PHB  |                             | Water<br>uptake(%) | Insoluble yield        |      |
|---------------|---------------|---------------|--------------|------|-----------------------------|--------------------|------------------------|------|
|               |               |               |              | (%)  | Ln[M <sub>0</sub> ]/<br>[M] |                    | in H <sub>2</sub> O(%) | (mg) |
| PHB-NIPAM-740 | 5             | 293           | 18.6         |      | 0.206                       | 156                | 80                     | 236  |
| PHB-NIPAM-741 | 10            | 368           | 33.6         | 52   | 0.41                        | 132                | 46                     | 170  |
| PHB-NIPAM-746 | 15            | 487           | 57.4         |      | 0.85                        | 173                | 47                     | 231  |
| PHB-NIPAM-742 | 20            | 533           | 66.6         | 34   | 1.10                        | 167                | 37                     | 197  |
| PHB-NIPAM-743 | 30            | 568           | 73.6         | 27   | 1.33                        | 239                | 35                     | 198  |
| PHB-NIPAM-744 | 42            | 617           | 83.4         | 29   | 1.80                        | 202                | 37                     | 227  |
| PHB-NIPAM-747 | 50            | 618           | 83.6         | 1.81 | 205                         | 51                 | 315                    |      |
| PHB-NIPAM-745 | 55            | 634           | 86.8         | 24   | 2.025                       | 248                | 24                     | 155  |

**Fig. 8** The plots for the monomer conversion (NIPAM) and PHB content in copolymer as a function of time. RAFT polymerization of NIPAM initiated by PHB-macro RAFT agent with AIBN at 70 °C

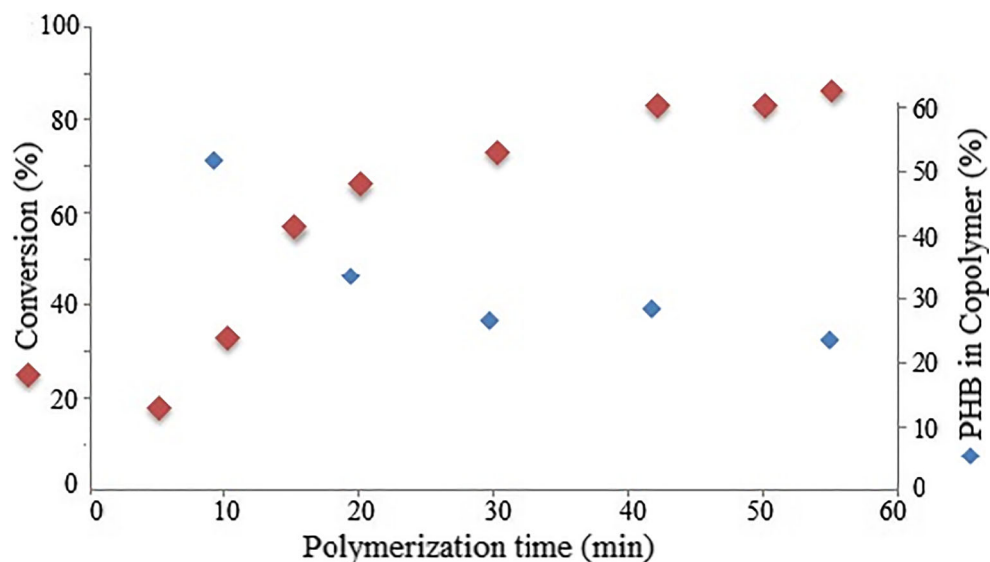

samples were studied by the determination of the micelle size by DLS. For the sample PHB-PNIPAM-2, micelles were measured by DLS. Without filtration, main peak can be distinguish, with a diameter of 744 nm represent 99% of the micelles and PDI of 0.511 (Fig. 7).

**Polymerization kinetics** The second set of experimental runs was established to evaluate the RAFT polymerization kinetics of NIPAM with the macro chain transfer agent, PHB-R2 at 70 °C (Table 3). The fixed PHB-R2, NIPAM and AIBN concentration in DMF solution, polymerization was carried out in different times starting from 5 min to 55 min. Polymer was recovered by precipitating in hexane after given polymerization times. From the Table 3, we can conclude that water uptake of the copolymer obtained increases as PNIPAM

content increases; and water solubility of the obtained copolymer increases as PNIPAM content increases.


Conversion of monomer to polymer was calculated by the equation below:

$$\text{Conversion}(\%) = \frac{[(\text{Yield}-200)]/500}{100} \times 100$$

Evolution of monomer conversion as a function of time with fixed chain transfer agent concentration in NIPAM polymerization at 70 °C was plotted in Fig. 8. The polymer yield increase proportionally by the time in the beginning. And then, the rate was retarded by the RAFT agent nearly the constant yield. As polymerization time increases, PHB content decreases similarly.

$\ln [M_0]/[M]$  was calculated using the  $[M_0] = 500$  mg and  $[M] = 500$  mg-(yield-200 mg) and plotted against


**Fig. 9** The plot of the  $\ln [M_0]/[M]$  of NIPAM as a function of time. ( $k = 6.86 \times 10^{-4}$  L/mols at 70 °C)

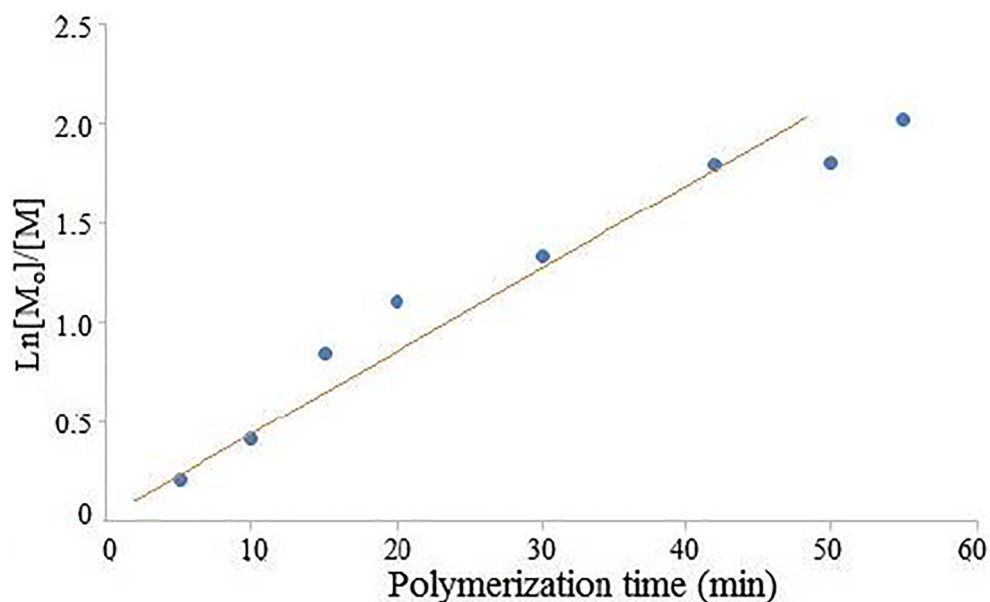

polymerization time. The data presented in Fig. 9 indicate that the conditions reported above lead to controlled living NIPAM polymerization. Slope of the

pseudo first order kinetic plot gives us the rate constant of the RAFT polymerization of NIPAM as  $k = 6.86 \times 10^{-4} \text{ L/mol s}$  at  $70^\circ\text{C}$ .

**Fig. 10** DSC curves of PHB-PNIPAM block copolymers: **a** PHB-PNIPAM-741, **b** PHB-PNIPAM-742, **c** PHB-PNIPAM-743, **d** PHB-PNIPAM-744, **e** PHB-PNIPAM-745, **f** PHB-DEA-281, **g** PHB-R2-131

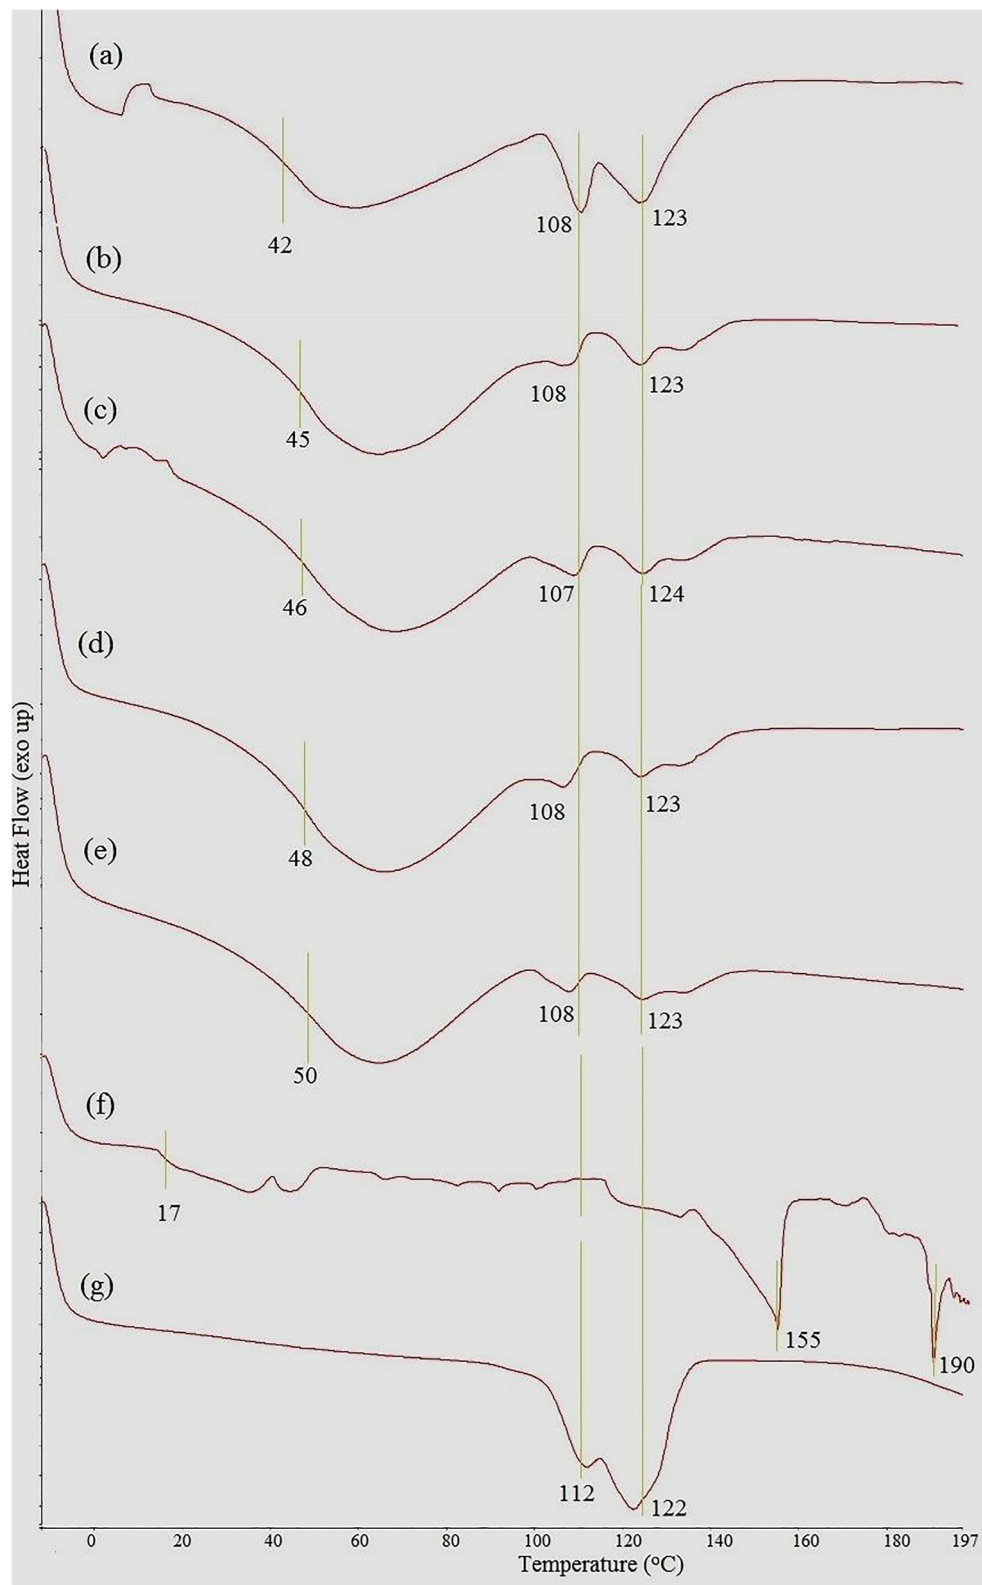

**DSC Thermal Analysis** was carried out using DSC to measure thermal behavior of the obtained copolymers of the second series in Table 3. DSC thermograms of the precursor PHB-DEA, PHB-R2 and the obtained PHB-PNIPAM copolymers. DSC traces of the polymers (Fig. 10), very wide T<sub>g</sub> and several T<sub>m</sub>s were observed. While pure PHB had a melting transition at around 170 °C, the PHB derivatives showed lower melting transitions. Increase in PNIPAM content in copolymer slightly increases the T<sub>g</sub> of PNIPAM in the copolymer. This result is in good agreement with the cited reference [43].

Several T<sub>m</sub>'s in DSC thermograms for poly-3-hydroxy alkanates in the modification reactions can be seen in some cited references [28, 34, 44, 45], as well. This small melting transition may result from different combinations of the block copolymer with the development of micro-heterogeneities.

## Conclusion

A member of commercially available microbial polyester, poly(3-hydroxy butyrate) derivatization opens a new gate to prepare PHB copolymers for medical applications. This novel PHB-macro raft agent makes possible to synthesis wide variety of the PHB derivatives. The carboxyl end of PHB was reacted with diethanol amine in order to obtain PHB with three hydroxyl functionalities in the chain ends. The hydroxyl ends were then reacted with the RAFT agent containing carboxylic acid end to prepare first time PHB-macro raft agent which was successfully initiated the polymerization of NIPAM. Because polymerization rate at 80 °C was very fast, the polymerization was conducted at 70 °C to study the kinetic parameters. Then, RAFT polymerization kinetics of NIPAM at 70 °C showed the typical controlled living polymerization aspects. Physicochemical characterization of the PHB-PNIPAM thermoresponsive block copolymer was investigated in detail.

**Acknowledgments** This work was supported by the Kapadokya University Research Funds (#KÜN.2018-BAGP-001) and Bülent Ecevit University Research Funds (#BEU-2017-72118496-01). The Authors thank to S. Hamadi (GPC) for technical assistance.

## References

1. Lenz RW, Marchessault RH (2005) Bacterial polyesters: biosynthesis, biodegradable plastics and biotechnology. *Biomacromolecules* 6:1–8
2. Sudesh K, Abe H, Doi Y (2000) Synthesis, structure and properties of polyhydroxyalkanoates: biological polyesters. *Prog Polym Sci* 25:1503–1555
3. Kocer H, Borcakli M, Demirel S, Hazer B (2003) Production of bacterial polyesters from some various new substrates by *Alcaligenes eutrophus* and *Pseudomonas oleovorans*. *Turkish J Chem* 27:365–374
4. Ashby RD, Foglia TA (1998) Poly (hydroxyalkanoate) biosynthesis from triglyceride substrates. Poly (hydroxyalkanoate) biosynthesis from triglyceride substrates. *Appl Microbiol Biotechnol* 49:431–437
5. Koray O, Koksall MS, Hazer B (2010) Simple production experiment of poly (3-hydroxy butyrate) for science laboratories and its importance for science process skills of prospective teachers. *Energy Educ Sci Technol Part B-Social Educational Studies* 2(1–2):39–54
6. Chen GQ (2009) A microbial polyhydroxyalkanoates (PHA) based bio- and materials industry. *Chem Soc Rev* 38:2434–2446
7. Gross RA, DeMello C, Lenz RW, Brandl H, Fuller RC (1989) The biosynthesis and characterization of poly(β-hydroxyalkanoates) produced by *Pseudomonas oleovorans*. *Macromolecules* 22:1106–1115
8. Hazer B, Lenz RW, Fuller RC (1994) Biosynthesis of methyl branched poly (β-hydroxy alkanate)s with *Pseudomonas oleovorans*. *Macromolecules* 27:45–49
9. Li X, Loh XJ, Wang K, He C, Li J (2005) Poly(ester urethane)s consisting of poly[(R)-3-hydroxybutyrate] and poly(ethylene glycol) as candidate biomaterials: characterization and mechanical property study. *Biomacromolecules* 6:2740–2747
10. Michalak M, Kurcok P, Hakkarainen M (2017) Polyhydroxyalkanoate-based drug delivery systems. *Polym Int* 66:617–622
11. Hazer B, Steinbüchel A (2007) Increased diversification of polyhydroxyalkanoates by modification reactions for industrial and medical applications. *Appl Microbiol Biotechnol* 74:1–12
12. Hazer DB, Kilicay E, Hazer B (2012) Poly (3-hydroxyalkanoate)s: diversification and biomedical applications. A state of the art review. *Mater Sci Eng C* 32:637–647
13. Hazer DB, Hazer B (2011) The effect of gold clusters on the autoxidation of poly (3-hydroxy 10-undecenoate-co-3-hydroxy octanoate) and tissue response evaluation. *J Polym Res* 18:251–262
14. Hazer DB, Bal E, Nurlu G, Benli K, Balci S, Öztürk F, Hazer B (2013) In vivo application of poly-3-hydroxyoctanoate as peripheral nerve graft. *J Zhejiang University SCIENCE B* 14(11):993–1003
15. Rai R, Keshavarz T, Roether JA, Boccaccini AR, Roy I (2011) Medium chain length polyhydroxyalkanoates, promising new biomedical materials for the future. *Mater Sci Eng R Rep* 72:29–47
16. Raza ZA, Riaz S, Banat IM (2018) Polyhydroxyalkanoates: properties and chemical modification approaches for their functionalization. *Biotechnol Prog* 34:29–41
17. Hazer B (2015) Simple synthesis of amphiphilic poly (3-hydroxy alkanate)s with pendant hydroxyl and carboxylic groups via thiolene photo click reactions. *Polym Degrad Stab* 119:159–166
18. Le Fer G, Babinot J, Versace D-L, Langlois V, Renard E (2012) The amino end groups of Jeffamine were converted into thiol by a reaction with N-acetyl homocysteine thiolactone and subsequently photo grafted. *Macromol Rapid Commun* 33:2041–2045
19. Domenek S, Langlois V, Renard E (2007) Bacterial polyesters grafted with poly (ethylene glycol): behaviour in aqueous media. *Polym Degrad Stab* 92:1384–1392
20. Kılıçay E, Hazer B, Çoban B, Scholz C (2010) Synthesis and characterization of the poly (ethylene glycol) grafted unsaturated microbial polyesters. *Hacettepe J Biol Chem* 38:9–17
21. Jain-Beuguel C, Xue L, Houel-Renault L, Modjinou T, Simon-Colin C, Gref R, Renard E, Langlois V (2019) Water-soluble poly(3-hydroxyalkanoate) sulfonate: versatile biomaterials used as coatings for highly porous nano-metal organic framework. *Biomacromolecules* 20(20):3324–3332
22. Chen GQ, Albertsson AC (2019) Polyhydroxy alkanates and other biopolymers. *Biomacromolecules* 20:3211–3212

23. Sparks J, Scholz C (2008) Synthesis and characterization of a cationic poly ( $\beta$ -hydroxy alkanooate). *Biomacromolecules* 9:2091–2096
24. Ma YM, Wei DX, Yao H, Wu LP, Chen GQ (2016) Synthesis, characterization and application of thermoresponsive polyhydroxyalkanoate-graft-poly(*n*-isopropylacrylamide). *Biomacromolecules* 17:2680–2690
25. Cakmakli B, Hazer B, Borcakli M (2001) Poly (styrene peroxide) and poly (methyl methacrylate peroxide) for grafting on unsaturated bacterial polyesters. *Macromol Biosci* 1(8):348–354
26. Arkin AH, Hazer B, Borcakli M (2000) Chlorination of poly-3-hydroxy alkanooates containing unsaturated side chains. *Macromolecules* 33:3219–3223
27. Arkin AH, Hazer B (2002) Chemical modification of chlorinated microbial polyesters. *Biomacromolecules* 3(6):1327–1335
28. Yalcin B, Cakmak M, Arkin AH, Hazer B, Erman B (2006) Control of optical anisotropy at large deformations in PMMA/chlorinated-PHB (PHB-cl) blends: Mechano-optical behavior. *Polymer* 47: 8183–8193
29. Hazer B (2010) Amphiphilic poly (3-hydroxy alkanooate)s: potential candidates for medical applications. *Int J Polym Sci* 2010:423460. <https://doi.org/10.1155/2010/423460>
30. Loh XJ, Zhang Z-X, Wu Y-L, Lee TS, Li J (2009) Synthesis of novel biodegradable thermoresponsive triblock copolymers based on poly[(*r*)-3-hydroxybutyrate] and poly(*n*-isopropylacrylamide) and their formation of thermoresponsive micelles. *Macromolecules* 42:194–202
31. Wang K, Liow SS, Wu Q, Li C, Owh C, Li Z, Loh XJ, Wu Y-L (2017) Codelivery for paclitaxel and bcl-2 conversion gene by phb-pdmaema amphiphilic cationic copolymer for effective drug resistant cancer therapy. *Macromol Biosci* 17:1700186
32. Reeve MS, McCarthy SP, Gross RA (1990) Chemical degradation of bacterial polyesters for use in the preparation of new degradable block copolymers. *Prepr Am Chem Soc Div Polym Sci* 31(1):437–438
33. Hirt TD, Neuenschwander P, Suter UW (1996) Telechelic diols from poly [(*R*)-3-hydroxybutyric acid] and poly([(R)-3-hydroxybutyric acid]-co-[(R)-3-hydroxyvaleric acid]. *Macromol Chem Phys* 197: 1609–1614
34. Hazer B, Akyol E, Şanal T, Guillaume S, Çakmakli B, Steinbuechel A (2019) Synthesis of novel biodegradable elastomers based on poly [3 – hydroxy butyrate] and poly [3-hydroxy octanoate] via transamidation reaction. *Polym Bull* 2019(76):919–932
35. Erol A, Rosberg DBH, Hazer B, Göncü BS (2020) Biodegradable and biocompatible radiopaque iodinated poly-3-hydroxy butyrate. Synthesis, characterization and *in vitro/in vivo* x-ray visibility. *Polym Bull*. <https://doi.org/10.1007/s00289-019-02747-6>
36. Neugebauer D, Rydz J, Goebel I, Dacko P, Kowalczyk M (2007) Synthesis of graft copolymers containing biodegradable poly (3-hydroxybutyrate). *Macromolecules* 40:1767–1773
37. Hazer B, Arslan H, Senemoğlu Y, Şen Ş (2019) Synthesis of block/graft copolymers based on vinyl benzyl chloride via reversible addition fragmentation chain transfer (RAFT) polymerization using the carboxylic acid functionalized trithiocarbonate. *J Polym Res* 26: 101, 1–19
38. Neises B, Steglich W (1978) Simple method for the esterification of carboxylic acid. *Chem Int Ed* 17:522–524
39. Cheng J, Wang J (2009) Syntheses of amphiphilic biodegradable copolymers of poly(ethyl ethylene phosphate) and poly(3-hydroxybutyrate) for drug delivery. *Sci China Ser B Chem* 52(7): 961–968
40. Convertine AJ, Ayres N, Scales CW, Lowe AB, McCormick CL (2004) Facile, controlled, room-temperature RAFT polymerization of *N*-isopropylacrylamide. *Biomacromolecules* 5:1177–1180
41. Bandelli D, Weber C, Schubert US (2019) Strontium isopropoxide: a highly active catalyst for the ring-opening polymerization of lactide and various lactones. *Macromol Rapid Commun* 40: 1900306
42. Feil H, Bae YH, Feijen J, Kim SW (1993) Effect of comonomer hydrophilicity and ionization on the lower critical solution temperature of *N*-Isopropylacrylamide copolymers. *Macromolecules* 26: 2496–2500
43. Liu Y-Y, Lu J, Shao Y-H (2006) Preparation and characterization of poly(*N*-isopropylacrylamide)-modified poly(2-hydroxyethyl acrylate) hydrogels by interpenetrating polymer networks for sustained drug release. *Macromol Biosci* 6:452–458
44. Curley J, Hazer B, Lenz RW, Fuller RC (1996) Production of poly (3-hydroxyalkanoates) containing aromatic substituents by *Pseudomonas oleovorans*. *Macromolecules* 29:1762–1766
45. Toraman T, Hazer B (2014) Synthesis and characterization of the novel thermoresponsive conjugates based on poly (3-hydroxy alkanooates). *J Polym Environ* 22:159–166

**Publisher's note** Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.